

## Test Report

SPONSOR: **FabriTRAK Systems Inc.**  
Mount Laurel, NJ

**Sound Absorption**  
**RAL™-A20-302**

CONDUCTED: 2020-07-14

Page 1 of 8

ON: 1 in. Terra Core Poly Hi-Impact Infill (100% Polyester Infill) (Type A mounting)

### TEST METHODOLOGY

Riverbank Acoustical Laboratories™ is accredited by the U.S. Department of Commerce, National Institute of Standards and Technology (NIST) under the National Voluntary Laboratory Accreditation Program (NVLAP) as an ISO 17025:2017 Laboratory (NVLAP Lab Code: 100227-0) and for this test procedure. The test reported in this document conformed explicitly with ASTM C423-17: "Standard Test Method for Sound Absorption and Sound Absorption Coefficients by the Reverberation Room Method." The specimen mounting was performed according to ASTM E795-16: "Standard Practices for Mounting Test Specimens During Sound Absorption Tests." A description of the measurement procedure and room specifications are available upon request. The results presented in this report apply to the sample as received from the test sponsor.

### INFORMATION PROVIDED BY SPONSOR

The test specimen was designated by the sponsor as 1 in. Terra Core Poly Hi-Impact Infill (100% Polyester Infill) (Type A mounting). The following nominal product information was provided by the sponsor prior to testing. The accuracy of such sponsor-provided information can affect the validity of the test results.

#### Product Under Test

Trade Name: Terra Core Poly Hi-Impact Infill  
Material: 100 % polyester infill  
Thickness: 25.4 mm (1 in.)  
Manufacturer: FabriTRAK Systems Inc.

### SPECIMEN MEASUREMENTS & TEST CONDITIONS

Through a full external visual inspection performed on the test specimen, Riverbank personnel verified the following information:

#### Test Specimen

Material: Semirigid felt panels  
Dimensions: 4 @ 1219.2 mm (48 in.) x 1219.2 mm (48 in.)  
2 @ 304.8 mm (12 in.) x 1219.2 mm (48 in.)  
Thickness: 23.22 mm (0.914 in.)  
Overall Weight: 10.21 kg (22.5 lbs)  
Density: 65.72 kg/m<sup>3</sup> (4.10 lbs/ft<sup>3</sup>)

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

An  ALION Technical Center

RIVERBANK.ALIONSCIENCE.COM

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

## Test Report

FabriTRAK Systems Inc.  
2020-07-14

RAL™-A20-302  
Page 2 of 8

### Overall Specimen Properties

Size: 2.74 m (108.0 in) wide by 2.44 m (96.0 in) long  
Thickness: 0.02 m (0.914 in)  
Weight: 10.21 kg (22.5 lbs)  
Mass per Unit Area: 1.53 kg/m<sup>2</sup> (0.31 lbs/ft<sup>2</sup>)  
Calculation Area: 6.689 m<sup>2</sup> (72 ft<sup>2</sup>)

### Test Environment

Room Volume: 291.98 m<sup>3</sup>  
Temperature: 22.6 °C ± 0.1 °C (Requirement: ≥ 10 °C and ≤ 5 °C change)  
Relative Humidity: 58.6 % ± 0.0 % (Requirement: ≥ 40 % and ≤ 5 % change)  
Barometric Pressure: 98.7 kPa (Requirement not defined)

### MOUNTING METHOD

Type A Mounting: The test specimen was laid directly against the test surface. Perimeter edges were sealed with metal framing.

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

An **ALION** Technical Center

RIVERBANK.ALIONSCIENCE.COM

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

**Test Report**

**FabriTRAK Systems Inc.**  
2020-07-14

**RAL™-A20-302**  
Page 3 of 8

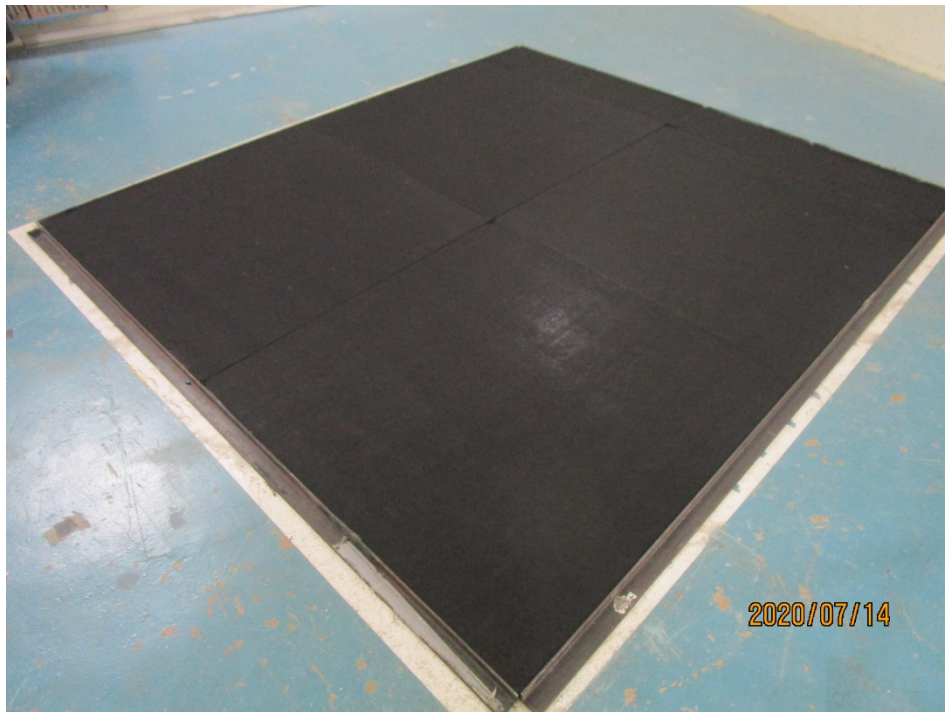


Figure 1 – Specimen mounted in test chamber



Figure 2 – Detail of specimen material

1512 S BATAVIA AVENUE  
 GENEVA, IL 60134  
 630-232-0104

An  ALION Technical Center

RIVERBANK.ALIONSCIENCE.COM

FOUNDED 1918 BY  
 WALLACE CLEMENT SABINE

## Test Report

**FabriTRAK Systems Inc.**  
 2020-07-14

**RAL™-A20-302**  
 Page 4 of 8

### TEST RESULTS

Specimen total absorption and absorption coefficient are tabulated at the eighteen standard frequencies. A graphic presentation of the data and additional information appear on the following pages.

1/3 Octave Center Frequency (Hz)	Total Absorption (m <sup>2</sup> )	Total Absorption (Sabins)	Absorption Coefficient
100	0.36	3.89	0.05
** 125	0.87	9.38	0.13
160	1.04	11.24	0.16
200	1.28	13.74	0.19
** 250	1.75	18.85	0.26
315	2.38	25.66	0.36
400	2.90	31.26	0.43
** 500	3.66	39.43	0.55
630	4.34	46.66	0.65
800	4.78	51.40	0.71
** 1000	5.15	55.46	0.77
1250	5.35	57.56	0.80
1600	5.59	60.13	0.84
** 2000	5.71	61.48	0.85
2500	6.04	64.98	0.90
3150	6.14	66.07	0.92
** 4000	6.21	66.83	0.93
5000	6.45	69.42	0.96

**SAA = 0.61**  
**NRC = 0.60**

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

An ALION Technical Center

RIVERBANK.ALIONSCIENCE.COM

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

## Test Report


FabriTRAK Systems Inc.  
2020-07-14

RAL™-A20-302  
Page 5 of 8


### TEST RESULTS (continued)

The sound absorption average (SAA) is defined in ASTM C423-17 Section 3.1.1 as the arithmetic average of the sound absorption coefficients of a material for the twelve one-third octave bands from 200 Hz through 2500 Hz, inclusive, rounded to the nearest integer multiple of 0.01.

The noise reduction coefficient (NRC) is defined from previous versions of ASTM C423 as the arithmetic average of the sound absorption coefficients at 250 Hz, 500 Hz, 1000 Hz, and 2000 Hz, rounded to the nearest integer multiple of 0.05.

Tested by   
Marc Sciaky  
Senior Experimentalist

Report by   
Malcolm Kelly  
Acoustical Test Engineer

Approved by   
Eric P. Wolfram  
Laboratory Manager

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

An ALION Technical Center

RIVERBANK.ALIONSCIENCE.COM

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

Test Report


FabriTRAK Systems Inc.  
2020-07-14

RAL™-A20-302

Page 6 of 8

SOUND ABSORPTION REPORT

1 in. Terra Core Poly Hi-Impact Infill (100% Polyester Infill) (Type A mounting)

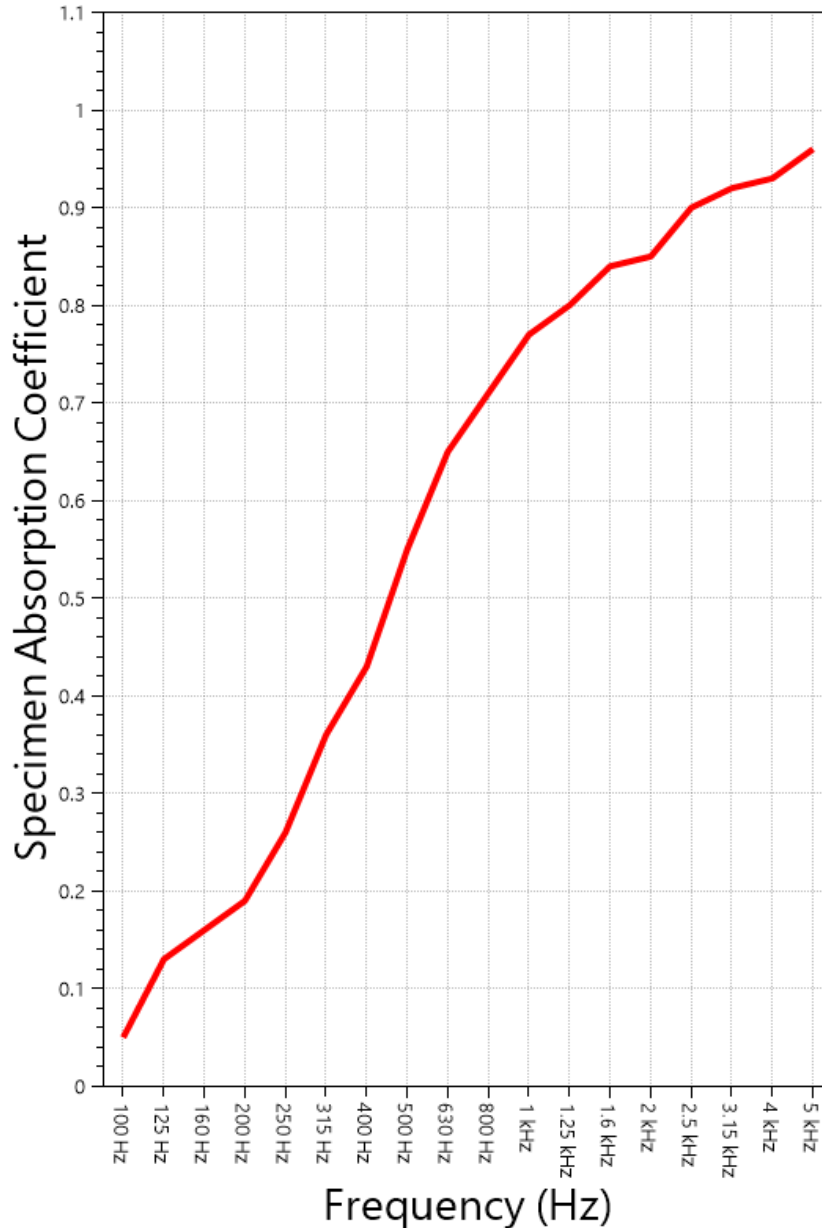

**SAA = 0.61**  
**NRC = 0.60**



RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

1512 S BATAVIA AVENUE  
 GENEVA, IL 60134  
 630-232-0104

An ALION Technical Center

RIVERBANK.ALIONSCIENCE.COM

FOUNDED 1918 BY  
 WALLACE CLEMENT SABINE

## Test Report

FabriTRAK Systems Inc.  
 2020-07-14

**RAL™-A20-302**  
 Page 7 of 8

### **APPENDIX A: Extended Frequency Range Data**

Specimen: 1 in. Terra Core Poly Hi-Impact Infill (100% Polyester Infill) (Type A mounting) (See Full Report)

*The following non-accredited data were obtained in accordance with ASTM C423-17, but extend beyond the defined frequency range of 100Hz to 5,000Hz. These unofficial results are representative of the RAL test environment only and intended for research & comparison purposes.*

1/3 Octave Band Center Frequency (Hz)	Total Absorption (Sabins)	Absorption Coefficient
31.5	-1.43	-0.02
40	-2.67	-0.04
50	4.28	0.06
63	7.46	0.10
80	-0.26	0.00
100	3.89	0.05
125	9.38	0.13
160	11.24	0.16
200	13.74	0.19
250	18.85	0.26
315	25.66	0.36
400	31.26	0.43
500	39.43	0.55
630	46.66	0.65
800	51.40	0.71
1000	55.46	0.77
1250	57.56	0.80
1600	60.13	0.84
2000	61.48	0.85
2500	64.98	0.90
3150	66.07	0.92
4000	66.83	0.93
5000	69.42	0.96
6300	69.36	0.96
8000	71.73	1.00
10000	76.67	1.06
12500	75.63	1.05

1512 S BATAVIA AVENUE  
GENEVA, IL 60134  
630-232-0104

An ALION Technical Center

RIVERBANK.ALIONSCIENCE.COM

FOUNDED 1918 BY  
WALLACE CLEMENT SABINE

## Test Report

FabriTRAK Systems Inc.  
2020-07-14

RAL™-A20-302  
Page 8 of 8

### APPENDIX B: Instruments of Traceability

Specimen: 1 in. Terra Core Poly Hi-Impact Infill (100% Polyester Infill) (Type A mounting) (See Full Report)

<u>Description</u>	<u>Model</u>	<u>Serial Number</u>	<u>Date of Certification</u>	<u>Calibration Due</u>
System 1	Type 3160-A-042	3160-106968	2020-06-26	2021-06-26
Bruel & Kjaer Mic And Preamp A	Type 4943-B-001	2311428	2019-09-27	2020-09-27
Bruel & Kjaer Pistonphone	Type 4228	2781248	2019-08-09	2020-08-09
Omega Digital Temp., Humid. And Pressure Recorder	OM-CP-PRHTemp2000	P97844	2020-02-18	2021-02-18

### APPENDIX C: Revisions to Original Test Report

Specimen: 1 in. Terra Core Poly Hi-Impact Infill (100% Polyester Infill) (Type A mounting) (See Full Report)

<u>Date</u>	<u>Revision</u>
2020-07-20	Original report issued

---

END